



## Synthesis, Crystal structure of hepta (pyridinium) bis (hexachlorobismuthate (III)) nitrate $[\text{C}_5\text{H}_6\text{N}]_7(\text{BiCl}_6)_2(\text{NO}_3)$

Fayçal Ben Tahar<sup>a\*</sup>, Perez Olivier<sup>b</sup>, Slaheddine Chaabouni<sup>a</sup>

<sup>a</sup>Laboratoire des Sciences de Matériaux et de l'Environnement (MESLab), Faculté des Sciences de Sfax (FSS), Université de Sfax, Route de Soukra - km 3,5 - BP 1171, 3018- Sfax, Tunisia.

E-mail address : [f\\_bentahar@yahoo.fr](mailto:f_bentahar@yahoo.fr); [chaabouni\\_slaheddine@yahoo.fr](mailto:chaabouni_slaheddine@yahoo.fr)

<sup>b</sup>Laboratoire CRISMAT, UMR 6508 CNRS, ENSICAEN- 6 Boulevard du Marechal Juin- 14050- Caen- Cedex 4- France.

E-mail address : [olivier.perez@ensicaen.fr](mailto:olivier.perez@ensicaen.fr)

### Abstract

An hepta (pyridinium) bis (hexachlorobismuthate (III)) nitrate,  $(\text{C}_5\text{H}_6\text{N})_7(\text{BiCl}_6)_2(\text{NO}_3)$  crystallizes at room temperature in the monoclinic system, space group  $P2_1/n$ , with the following unit-cell parameters:  $a = 9.555(1) \text{ \AA}$ ,  $b = 16.847(1) \text{ \AA}$ ,  $c = 32.522(1) \text{ \AA}$ ,  $\beta = 94.37^\circ$ ,  $V = 5219.8 \text{ \AA}^3$  and four molecules per unit cell. Its crystal structure was determined and refined down to  $R_1 = 0.0504$ ,  $wR_2 = 0.0667$ . The structure of the title compound,  $(\text{C}_5\text{H}_6\text{N})_7(\text{BiCl}_6)_2(\text{NO}_3)$  consists of seven monoprotonated pyridinium  $(\text{C}_5\text{H}_6\text{N})^+$  cations, two independent octahedron  $[\text{BiCl}_6]^{3-}$  and an isolated  $\text{NO}_3^-$  anion. These entities are linked together through  $\text{N-H}\cdots\text{Cl}$  and  $\text{N-H}\cdots\text{O}$  hydrogen bonds, originating from the  $(\text{C}_5\text{H}_6\text{N})^+$  groups and the isolated anion of nitrate to forming a three dimensional network.

### Indexing terms/Keywords

Organic-inorganic hybrid material; Crystal structure; Halogenobismuthates(III)

\* **Corresponding author:** Dr. Ben Tahar Fayçal

**Tel:** 21698949214, **Fax:** 21674274437

**E-mail address:** [f\\_bentahar@yahoo.fr](mailto:f_bentahar@yahoo.fr)

**Address:** Soukra Road - km 3.5 - B.P. 1171, 3018 Sfax - Tunisia

# Council for Innovative Research

Peer Review Research Publishing System

**Journal:** Journal of Advances in Chemistry

Vol. 9, No. 2

[editorjaconline@gmail.com](mailto:editorjaconline@gmail.com)

[www.cirworld.org/journals](http://www.cirworld.org/journals)



## I. Introduction

Halogenoantimonates(III) and halogenobismuthates(III) containing various organic cations form a large class of the organic– inorganic hybrid materials [1–5]. These molecular-ionic crystals are built up of the inorganic anions and organic cations. The compounds form various anionic structures in the solid state. The anionic sublattice is built up of either the simple discrete octahedra or one-dimensional chains or two- or three-dimensional anionic framework. In the majority of these hybrid materials the anionic moieties are rigid, whereas the organic cations, placed in large cavities of the anionic substructure, exhibit usually reorientational disorder.

The halogenoantimonates (III) and halogenobismuthates (III) evoke much interest because their single crystals exhibit the polar, non-linear or ferroic properties. The change in the dynamical state of cations is responsible for the mechanisms of the numerous structural phase transitions found in these materials. Such a mechanism of structural phase transitions was classified as ‘order–disorder’. A long range ferroelectric order of the dipoles has been found in the compounds containing generally the small in size ammonium cations (like monomethyl-, dimethyl- or trimethyl-ammonium) [6–10].

A novel group of crystals, containing heteroaromatic cations like: pyridinium, substituted pyridinium and imidazolium ones, have been recently synthesized and characterized [11–13]. Since aromatic heterocyclic cations are bestowed a significant electric dipole moment thus some halogenoantimonates (III) and halogenobismuthates (III) containing these cations form strongly polar structures. We have studied three pyridinium halogenobismuthates (III), i.e.  $(C_5H_5NH)_6Bi_4Cl_{18}$  [14],  $(C_5H_5NH)BiCl_4$  [15] and  $(C_5H_5NH)_5Bi_2Br_{11}$  [16]. The ferroelectricity was found, however, only in the compound of the  $R_5Bi_2X_{11}$  composition,  $(C_5H_5NH)_5Bi_2Br_{11}$ . This latter compound is a ferroelectric below the Curie temperature of 118 K. Among a dozen of the substituted pyridinium compounds, studied so far, a ferroelectricity is confirmed merely in a case of 4-aminopyridinium tetrachloroantimonate (III),  $(4-NH_2C_5H_4NH)SbCl_4$  [17], below  $T_c = 270.5$  K. The presence of polar properties in the materials described above is usually a result of the organic cations dynamics, which play a key role in the induction of ferroelectricity. The results, obtained by us for the group of ionic compounds containing aromatic cations, trace a direction of search for the novel polar materials.


Herein we report the synthesis and the crystal structural characterization by X-ray diffraction of the hepta (pyridinium) bis (hexachlorobismuthate (III)) nitrate.

## II. Experimental section

### II.1. Synthesis

Transparents and colorless crystals of  $[C_5H_5NH]_7(BiCl_6)_2(NO_3)$  were synthesized by the addition of pyridinium to a solution of bismuth (III) nitrate (molar ratio 7/2) in concentrated hydrochloric acid (36%). Single crystals were grown by the slow evaporation of an aqueous solution at room temperature.

The chemical reaction of the title compound was the following :



### II.2. Single crystal Structure determination

X-ray data collection was carried out on a Bruker Kappa Apex II CCD diffractometer with graphite monochromated  $Mo K\alpha$  radiation. Bismuth and chlorine atoms positions were located using the direct method with program SHELXS-97 [18] program, while the carbon, oxygen, and nitrogen atoms were found from successive difference Fourier calculations using SHELXL97 [19] computer program. The structure is refined by full matrix least-squares using anisotropic temperature factors for all non-hydrogen atoms. All hydrogen atoms were geometrically fixed at the calculated positions attached to their parent atoms and treated as riding atoms. Crystal data, collected reflections, and parameters of the final refinement are reported in Table 1.

**Table 1:** Experimental data for X-ray diffraction study of  $[C_5H_5NH]_7(BiCl_6)_2(NO_3)$

Crystal data	
Empirical formula	$C_{35}H_{42}Bi_2Cl_{12}N_8O_3$
Formula weight (g/mol)	1466,13
Crystal system, Space group	monoclinic, $P2_1/n$
$a$ (Å)	9.555(1)
$b$ (Å)	16.847(1)
$c$ (Å)	32.522(1)
$\beta$	94.37(1)°
$V$ (Å <sup>3</sup> )	5219.8(0)
$Z$	4




$D_{\text{calc}}$ (g cm <sup>-3</sup> )	1.866
$\mu$ (mm <sup>-1</sup> )	7.389
$F(000)$	2808
Crystal size (mm)	0.25 × 0.20 × 0.15
Crystal habit	Colorless
<i>Data collection</i>	
Diffractometer	BrukerKappaApex II CCD diffractometer Graphite
Monochromator	Mo-K $\alpha$ , 0.71073
Radiation type, $\lambda$ (Å)	293(2)
$T$ (K)	1.26 - 34.99
$\Theta$ Range (°)	$-11 \leq h \leq 15$
Indexes range	$-26 \leq k \leq 27$ $-52 \leq l \leq 51$
Absorption correction	numerical 0.2595/0.4036
$T_{\text{min}}/T_{\text{max}}$	84321
Measured reflections	21099
Independent reflections	12702
Observed refl. ( $I > 2\sigma(I)$ )	0.0354
$R_{\text{int}}$	
<i>Refinement</i>	
Refinement on	$F^2$ 21099/5/541
Data/restraints/parameters	$R1 = 0.0504$
$R(F_o^2) > 2\sigma(F_o^2)$	$wR2 = 0.0667$ 1.021
Goof = S	926364
CCDC deposition number	

### III. Results and discussion

The final atomic coordinates obtained from the single crystal refinement with  $U_{\text{eq}}$  are given in Table 2. The anisotropic displacement parameters are shown in Table 3. Interatomic distances and bond angles schemes are listed in Table 4.

The asymmetric unit of our component,  $[\text{C}_5\text{H}_5\text{NH}]_7(\text{BiCl}_6)_2(\text{NO}_3)$ , consists of two distinct octahedra  $[\text{BiCl}_6]^{3-}$ , isolated  $\text{NO}_3^-$  anion and seven monoprotonated pyridinium cations as shown in Fig. 1.

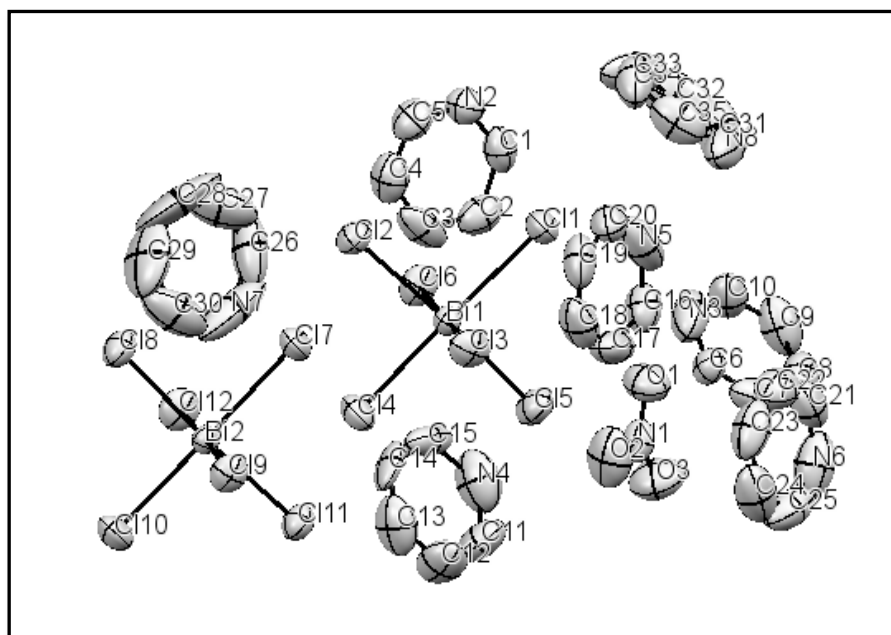

**Figure 1** : The asymmetric unit of  $[\text{C}_5\text{H}_5\text{NH}]_7(\text{BiCl}_6)_2(\text{NO}_3)$ , showing the atom-numbering scheme

**Table 2:** Atomic coordinates and  $U_{\text{eq}}$  or  $U_{\text{iso}}$  for  $[\text{C}_5\text{H}_5\text{NH}]_7(\text{BiCl}_6)_2(\text{NO}_3)$

Atomes	x	y	z	$U_{\text{eq}}$
Bi1	0.044479(13)	0.648857(9)	0.285559(4)	0.03835(4)
Bi2	0.758222(13)	0.740706(8)	0.491828(4)	0.03762(4)
Cl1	0.21692(11)	0.72253(8)	0.23300(4)	0.0634(3)
Cl2	0.26306(10)	0.57334(7)	0.32870(4)	0.0562(3)
Cl3	0.03392(12)	0.51559(8)	0.23403(4)	0.0674(3)
Cl4	-0.12433(11)	0.57297(8)	0.33372(4)	0.0654(3)
Cl5	-0.18081(11)	0.71957(8)	0.24617(4)	0.0687(3)
Cl6	0.07738(12)	0.76756(7)	0.33769(4)	0.0638(3)
Cl7	0.93579(11)	0.81443(8)	0.44270(4)	0.0613(3)
Cl8	-0.99095(11)	0.67426(8)	0.53184(4)	0.0628(3)
Cl9	0.73347(11)	0.61258(7)	0.44107(4)	0.0600(3)
Cl10	0.58374(12)	0.67365(8)	0.54308(4)	0.0713(3)
Cl11	0.54242(10)	0.80979(7)	0.44775(3)	0.0576(3)
Cl12	0.77755(13)	0.86515(8)	0.54412(4)	0.0687(3)
O1	0.9038(4)	0.6237(2)	0.13693(14)	0.0905(12)
O2	0.7792(5)	0.5196(3)	0.13845(15)	0.1150(16)
O3	0.6832(4)	0.6313(3)	0.13652(16)	0.1136(16)
N1	0.7854(5)	0.5915(3)	0.13727(12)	0.0613(10)
N2	0.1329(4)	0.5251(3)	0.13220(14)	0.0719(12)
N3	0.9661(6)	0.8279(5)	0.15846(17)	0.124(2)
N4	-0.1099(8)	0.3541(3)	0.1720(2)	0.120(2)
N5	0.4614(9)	0.5583(4)	0.24511(18)	0.127(2)
N6	0.6850(9)	0.6524(5)	0.02821(18)	0.120(2)





N7	0.0986(12)	0.6144(10)	0.4288(3)	0.172(6)
N8	0.3469(6)	0.8201(7)	0.12434(18)	0.138(3)
C1	0.2495(6)	0.5616(3)	0.14554(16)	0.0712(14)
C2	0.3759(5)	0.5293(4)	0.13689(17)	0.0733(15)
C3	0.3771(6)	0.4615(4)	0.11502(19)	0.0830(18)
C4	0.2538(8)	0.4267(4)	0.10216(19)	0.0875(18)
C5	0.1343(6)	0.4592(4)	0.11105(19)	0.0799(16)
C6	0.8686(5)	0.7878(3)	0.13562(15)	0.0535(11)
C7	0.7845(6)	0.8221(4)	0.10967(19)	0.0846(18)
C8	0.7904(7)	0.9002(5)	0.1028(2)	0.093(2)
C9	0.8847(8)	0.9434(4)	0.1248(2)	0.0944(19)
C10	0.9742(7)	0.9101(4)	0.1522(2)	0.0860(18)
C11	0.0079(6)	0.3152(5)	0.1838(2)	0.0905(19)
C12	0.0230(7)	0.2424(4)	0.1745(2)	0.100(2)
C13	-0.0809(11)	0.2038(4)	0.1528(2)	0.109(2)
C14	-0.1941(7)	0.2402(5)	0.14071(17)	0.0782(18)
C15	-0.2143(5)	0.3122(6)	0.14944(19)	0.093(2)
C16	0.6059(7)	0.5551(4)	0.24427(18)	0.0833(17)
C17	0.6649(6)	0.4874(6)	0.2394(2)	0.099(2)
C18	0.5848(9)	0.4206(4)	0.2348(2)	0.101(2)
C19	0.4452(8)	0.4273(5)	0.23570(18)	0.095(2)
C20	0.3864(5)	0.4934(5)	0.24094(17)	0.0741(16)
C21	0.8287(10)	0.6546(5)	0.0283(2)	0.099(2)
C22	0.8972(6)	0.5873(7)	0.0326(2)	0.105(3)
C23	0.8251(10)	0.5196(5)	0.0359(2)	0.104(2)
C24	0.6870(11)	0.5219(5)	0.0358(2)	0.107(2)
C25	0.6207(7)	0.5877(7)	0.0319(2)	0.101(2)
C26	0.213(2)	0.6586(5)	0.4292(3)	0.149(5)
C27	0.3274(12)	0.6302(9)	0.4465(4)	0.148(4)
C28	0.3240(13)	0.5630(10)	0.4632(4)	0.175(6)
C29	0.214(2)	0.5197(5)	0.4640(4)	0.147(4)
C30	0.1049(12)	0.5468(10)	0.4470(5)	0.151(5)
C31	0.3605(13)	0.8918(7)	0.1470(4)	0.141(5)
C32	0.4364(14)	0.8937(5)	0.1794(4)	0.134(4)
C33	0.5117(8)	0.8355(9)	0.1913(3)	0.132(4)
C34	0.5117(8)	0.7712(6)	0.1724(3)	0.109(3)
C35	0.4306(9)	0.7609(4)	0.1390(3)	0.100(2)
H1	0.2464	0.6085	0.1606	0.085
H2	0.0535	0.5452	0.1376	0.086
H2A	0.4596	0.5539	0.1460	0.088
H3	1.0221	0.8043	0.1764	0.149



H311	0.4617	0.4388	0.1088	0.100
H4	0.2533	0.3799	0.0870	0.105
H4A	-0.1206	0.4033	0.1780	0.143
H5	0.0499	0.4349	0.1022	0.096
H5A	0.4207	0.6032	0.2484	0.152
H6	0.8624	0.7331	0.1389	0.064
H6A	0.6381	0.6959	0.0256	0.144
H7	0.7162	0.7921	0.0948	0.102
H7A	0.0210	0.6308	0.4165	0.206
H8	0.7290	0.9239	0.0829	0.112
H8A	0.2894	0.8149	0.1028	0.165
H9	0.8877	0.9980	0.1207	0.113
H10	1.0415	0.9405	0.1672	0.103
H11	0.0800	0.3415	0.1991	0.109
H12	0.1059	0.2160	0.1828	0.121
H13	-0.0705	0.1504	0.1464	0.131
H14	-0.2638	0.2129	0.1250	0.094
H15	-0.2986	0.3369	0.1408	0.112
H16	0.6596	0.6011	0.2472	0.100
H17	0.7619	0.4841	0.2390	0.119
H18	0.6261	0.3714	0.2311	0.122
H19	0.3900	0.3820	0.2324	0.113
H20	0.2894	0.4959	0.2418	0.089
H21	0.8760	0.7022	0.0253	0.119
H22	0.9947	0.5866	0.0335	0.126
H23	0.8721	0.4713	0.0382	0.124
H24	0.6372	0.4750	0.0387	0.128
H25	0.5234	0.5879	0.0317	0.122
H26	0.2106	0.7087	0.4173	0.179
H27	0.4107	0.6588	0.4468	0.178
H28	0.4074	0.5433	0.4758	0.210
H29	0.2163	0.4703	0.4768	0.177
H30	0.0232	0.5169	0.4473	0.182
H31	0.3127	0.9371	0.1376	0.169
H32	0.4381	0.9394	0.1955	0.161
H33	0.5699	0.8407	0.2154	0.158
H34	0.5703	0.7303	0.1822	0.131
H35	0.4305	0.7126	0.1251	0.120

**Table 3:** Anisotropic displacement parameters ( $\text{\AA}^2$ ) for  $[\text{C}_5\text{H}_5\text{NH}]_7(\text{BiCl}_6)_2(\text{NO}_3)$ 


Atomes	U11	U22	U33	U23	U13	U12
Bi1	0.03903(6)	0.03560(8)	0.04035(8)	-0.00004(6)	0.00259(5)	0.00134(5)
Bi2	0.03866(6)	0.03664(8)	0.03720(8)	-0.00024(6)	0.00053(5)	-0.00083(5)
Cl1	0.0552(5)	0.0708(8)	0.0650(8)	0.0167(6)	0.0102(5)	-0.0056(5)
Cl2	0.0532(5)	0.0518(7)	0.0620(7)	-0.0001(5)	-0.0065(4)	0.0048(4)
Cl3	0.0723(7)	0.0695(9)	0.0600(8)	-0.0228(6)	0.0038(5)	-0.0137(6)
Cl4	0.0614(6)	0.0656(8)	0.0722(8)	0.0154(6)	0.0241(5)	0.0009(5)
Cl5	0.0591(6)	0.0618(8)	0.0824(9)	0.0115(7)	-0.0123(5)	0.0068(5)
Cl6	0.0799(7)	0.0497(7)	0.0601(8)	-0.0154(6)	-0.0061(5)	0.0071(5)
Cl7	0.0565(5)	0.0751(8)	0.0535(7)	0.0127(6)	0.0114(5)	-0.0121(5)
Cl8	0.0557(5)	0.0717(8)	0.0594(7)	0.0065(6)	-0.0069(5)	0.0126(5)
Cl9	0.0707(6)	0.0483(7)	0.0596(7)	-0.0137(6)	-0.0043(5)	0.0006(5)
Cl10	0.0670(6)	0.0819(9)	0.0672(8)	0.0136(7)	0.0194(5)	-0.0176(6)
Cl11	0.0535(5)	0.0605(7)	0.0574(7)	0.0041(6)	-0.0039(4)	0.0120(5)
Cl12	0.0847(7)	0.0591(8)	0.0614(8)	-0.0239(6)	0.0001(6)	0.0011(6)
O1	0.070(2)	0.076(3)	0.128(4)	0.011(2)	0.020(2)	0.0118(19)
O2	0.175(4)	0.053(3)	0.113(4)	0.005(3)	-0.013(3)	-0.004(3)
O3	0.070(2)	0.108(4)	0.162(5)	-0.012(3)	0.004(3)	0.015(2)
N1	0.080(3)	0.041(3)	0.062(3)	-0.001(2)	0.001(2)	0.008(2)
N2	0.063(2)	0.079(3)	0.074(3)	0.005(3)	0.012(2)	0.006(2)
N3	0.107(4)	0.186(7)	0.080(4)	0.045(4)	0.012(3)	0.061(4)
N4	0.165(6)	0.072(4)	0.125(5)	-0.005(4)	0.036(5)	0.010(4)
N5	0.193(7)	0.105(6)	0.084(4)	0.004(4)	0.024(4)	0.076(5)
N6	0.151(6)	0.121(6)	0.085(4)	-0.007(4)	-0.011(4)	0.065(5)
N7	0.142(7)	0.247(13)	0.117(7)	-0.058(8)	-0.056(6)	0.130(8)
N8	0.080(4)	0.270(11)	0.064(4)	0.019(6)	0.005(3)	0.000(5)
C1	0.097(4)	0.054(3)	0.063(3)	-0.009(3)	0.002(3)	0.001(3)
C2	0.065(3)	0.080(4)	0.073(4)	0.015(3)	-0.004(2)	-0.010(3)
C3	0.092(4)	0.081(5)	0.079(4)	0.023(4)	0.022(3)	0.041(3)
C4	0.130(5)	0.052(4)	0.079(4)	-0.008(3)	0.001(4)	0.013(3)
C5	0.088(4)	0.067(4)	0.083(4)	-0.003(3)	-0.008(3)	-0.020(3)
C6	0.066(3)	0.035(3)	0.059(3)	0.005(2)	0.001(2)	-0.0001(2)
C7	0.068(3)	0.101(5)	0.085(4)	-0.018(4)	0.008(3)	-0.020(3)
C8	0.090(4)	0.108(6)	0.080(5)	0.008(4)	-0.004(3)	0.031(4)
C9	0.142(6)	0.057(4)	0.088(5)	0.010(4)	0.028(4)	0.015(4)
C10	0.108(4)	0.071(4)	0.078(4)	-0.006(4)	-0.004(3)	-0.028(3)
C11	0.069(3)	0.090(5)	0.108(5)	-0.003(4)	-0.025(3)	-0.014(3)
C12	0.091(4)	0.081(5)	0.125(6)	0.001(4)	-0.021(4)	0.033(4)
C13	0.185(8)	0.042(4)	0.103(6)	-0.016(4)	0.031(5)	-0.004(4)
C14	0.085(4)	0.093(5)	0.054(3)	-0.015(3)	-0.010(3)	-0.052(4)



C15	0.048(3)	0.166(7)	0.065(4)	0.026(5)	-0.001(2)	0.020(4)
C16	0.098(4)	0.070(4)	0.082(4)	-0.008(3)	0.008(3)	-0.027(3)
C17	0.056(3)	0.146(7)	0.096(5)	-0.001(5)	0.006(3)	0.015(4)
C18	0.141(6)	0.074(5)	0.092(5)	-0.002(4)	0.026(4)	0.039(4)
C19	0.134(6)	0.095(6)	0.056(4)	-0.021(4)	0.019(4)	-0.048(4)
C20	0.060(3)	0.097(5)	0.066(4)	-0.015(4)	0.009(2)	-0.006(3)
C21	0.140(7)	0.086(5)	0.074(5)	0.006(4)	0.025(4)	-0.027(5)
C22	0.064(3)	0.172(9)	0.080(5)	-0.015(5)	0.012(3)	0.016(5)
C23	0.142(7)	0.088(6)	0.079(5)	-0.003(4)	-0.008(4)	0.046(5)
C24	0.143(7)	0.101(6)	0.074(5)	-0.008(4)	0.001(4)	-0.039(5)
C25	0.071(4)	0.133(8)	0.098(5)	-0.022(6)	-0.002(3)	-0.004(5)
C26	0.301(17)	0.061(6)	0.091(7)	0.033(5)	0.053(10)	0.037(8)
C27	0.118(7)	0.138(10)	0.191(13)	-0.049(9)	0.029(7)	-0.075(7)
C28	0.143(9)	0.186(13)	0.179(11)	-0.016(11)	-0.095(9)	0.076(8)
C29	0.232(13)	0.068(6)	0.146(10)	0.030(6)	0.040(10)	0.001(8)
C30	0.087(6)	0.180(12)	0.192(14)	-0.076(10)	0.046(7)	-0.064(7)
C31	0.172(10)	0.102(8)	0.162(10)	0.069(7)	0.093(8)	0.089(7)
C32	0.176(11)	0.051(5)	0.184(12)	-0.044(7)	0.082(8)	-0.013(5)
C33	0.090(5)	0.214(12)	0.092(6)	-0.067(8)	0.008(4)	-0.036(6)
C34	0.109(5)	0.134(8)	0.087(6)	0.045(5)	0.029(4)	0.048(5)
C35	0.116(6)	0.056(4)	0.132(7)	-0.023(4)	0.042(5)	-0.010(4)

A projection of the structure on the (100) plane (Fig. 2) shows that each bismuth is surrounded by six Cl atoms, forming a distorted octahedral configuration, with Bi-Cl distances range from 2.6251(11) to 2.7990(12) Å for the first octahedron and from 2.6852 (10) to 2.7295(10) Å for the second octahedron (see Table 4). These values are comparable with those reported by other researchers [20]. In addition to the bond-lengths differences, the Cl-Bi-Cl angles within each  $[\text{BiCl}_6]^{3-}$  anion extend from 85.72 (4) to 94.52 (4)° and from 86.87(4) to 93.04(4)° for cis and from 174.20(4) to 177.48(4)° and 175.42(4) to 177.99(4)° for trans arrangements. These values, which they listed in Table 4, do not indicate any stereochemical activity of the Bi lone electron pair [20,21] but this distortion is correlated to deformations resulting from strong hydrogen bond interactions [20,21], which involves all coordinated chlorine atoms [21]. The isolated nitrate anions play an important role in cohesion of the structure so they are located in the gaps left between the octahedra of bismuth and monoprotonated organic cations. In fact, the presence of those anions as a part of an anionic sublattice in the family of organic – inorganic hybrids was also found in other structure [22,23]. The seven organic template cations,  $[\text{C}_5\text{H}_5\text{NH}]^+$ , reside within the crystal lattice and maintain the charge neutrality (see Fig. 1). Also, the C-N bond lengths in organic cations are ranging 1.467 (12) - 1.504 (10) Å (see Table 4). The observed C-C distances in pyridinium are extended from 1.481 (16) to 1.533 (13) Å (see Table 4). These values are comparable with those reported by other researchers [24]. Besides in this compound, the aromatic rings built up by (C1,C2,C3,C4,C5,N2), (C11,C12,C13,C14,C15,N4) and (C16,C17,C18,C19,C20,N5) (rms deviation of fitted atoms equal to 0.0007 ; 0.0033 and 0.0046 respectively) are more planar than those built up by (C6,C7,C8,C9,C10,N3), (C21,C22,C23,C24,C25,N6), (C26,C27,C28,C29,C30,N7) and (C31,C32,C33,C34,C35,N8) (rms deviation of fitted atoms equal to 0.0052 ; 0.0053 ; 0.0077 and 0.0180 respectively).



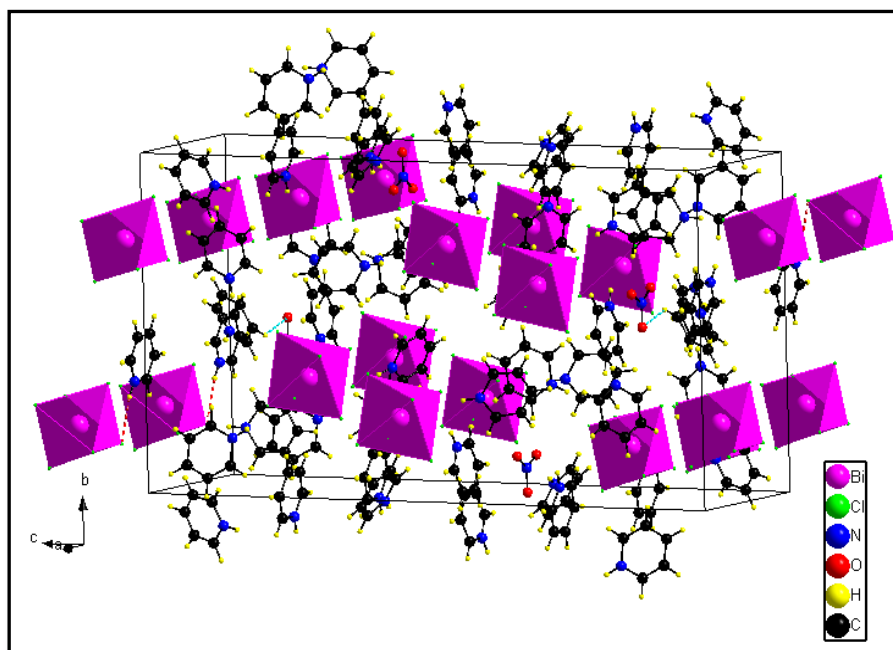

**Figure 2 :** Crystal packing of the  $[\text{C}_5\text{H}_5\text{NH}]_7(\text{BiCl}_6)_2(\text{NO}_3)$

**Table 4:** Selected bond (Å) lengths and angles (°) for  $[\text{C}_5\text{H}_5\text{NH}]_7(\text{BiCl}_6)_2(\text{NO}_3)$

Bi1-Cl1	2.7580(11)	N1-O1	1.255(5)
Bi1-Cl2	2.7390(10)	N1-O2	1.213(5)
Bi1-Cl3	2.7989(12)	N1-O3	1.184(5)
Bi1-Cl4	2.6597(11)	N2-C1	1.317(6)
Bi1-Cl5	2.6969(11)	C1-C2	1.373(7)
Bi1-Cl6	2.6251(11)	C2-C3	1.347(8)
Bi2-Cl7	2.7179(10)	C3-C4	1.353(9)
Bi2-Cl8	2.7295(10)	N2-C5	1.307(7)
Bi2-Cl9	2.7167(11)	C4-C5	1.318(8)
Bi2-Cl10	2.6938(11)	N3-C6	1.330(8)
Bi2-Cl11	2.6853(10)	C6-C7	1.261(7)
Bi2-Cl12	2.6970(12)	C7-C8	1.336(9)
		C8-C9	1.324(9)
		N3-C10	1.403(9)
		C9-C10	1.314(9)
		C11-N4	1.334(8)
		C11-C12	1.274(8)
		C12-C13	1.343(10)
		C13-C14	1.279(9)
		N4-C15	1.385(9)
		C14-C15	1.264(9)
		C16-N5	1.385(9)
		C16-C17	1.287(9)




		C17 -C18	1.362(9)
		C18-C19	1.341(9)
		C19-C20	1.264(9)
		C20-N5	1.308(8)
		N6-C21	1.374(10)
		C21-C22	1.310(10)
		C22-C23	1.342(10)
		C23-C24	1.320(10)
		N6-C25	1.261(9)
		C24-C25	1.278(10)
		N7-C26	1.320(14)
		C26-C27	1.283(14)
		C27-C28	1.256(10)
		C28-C29	1.283(12)
		N7-C30	1.283(14)
		C29-C30	1.230(12)
		N8-C31	1.416(13)
		C31-C32	1.233(13)
		C32-C33	1.260(13)
		C33-C34	1.246(11)
		N8-C35	1.343(10)
		C34-C35	1.297(11)
CI6-Bi1-CI4	91.94(4)	O3-N1-O2	121.6(5)
CI6-Bi1-CI5	91.28(4)	O3-N1-O1	119.8(5)
CI4-Bi1-CI5	89.66(4)	O2-N1-O1	118.6(5)
CI6-Bi1-CI2	88.50(3)	C5-N2-C1	121.8(5)
CI4-Bi1-CI2	87.02(3)	C7-C6-N3	121.7(5)
CI5-Bi1-CI2	176.67(4)	N2-C1-C2	118.8(5)
CI6-Bi1-CI1	90.56(4)	C3-C2-C1	119.2(5)
CI4-Bi1-CI1	177.48(4)	C12-C11-N4	120.8(6)
CI5-Bi1-CI1	89.98(4)	C15-C14-C13	122.1(5)
CI2-Bi1-CI1	93.34(3)	C6-N3-C10	117.7(5)
CI6-Bi1-CI3	174.19(4)	C9-C8-C7	119.1(6)
CI4-Bi1-CI3	88.35(4)	C2-C3-C4	119.2(5)
CI5-Bi1-CI3	94.52(4)	C9-C10-N3	118.6(6)
CI2-Bi1-CI3	85.72(4)	C6-C7-C8	122.0(6)
CI1-Bi1-CI3	89.19(4)	C10-C9-C8	120.9(6)
CI11-Bi2-CI10	91.48(4)	N2-C5-C4	120.8(5)
CI11-Bi2CI12	90.72(4)	C5-C4-C3	120.1(6)
CI10-Bi2-CI12	87.23(4)	C11-N4-C15	117.4(6)
CI11-Bi2-CI9	89.56(4)	C14-C15-N4	119.4(5)



Cl10-Bi2-Cl9	90.77(4)	C11-C12-C13	119.9(6)
Cl12-Bi2-Cl9	177.99(4)	C14-C13-C12	120.2(6)
Cl11-Bi2-Cl7	88.65(3)	C19-C20-N5	120.3(6)
Cl10-Bi2-Cl7	177.21(4)	C17-C16-N5	119.0(6)
Cl12-Bi2-Cl7	89.98(4)	C19-C18-C17	118.6(6)
Cl9-Bi2-Cl7	92.02(4)	C20-C19-C18	122.0(6)
Cl11-Bi2-Cl8	175.42(4)	C16-C17-C18	119.9(6)
Cl10-Bi2-Cl8	93.05(4)	C20-N5-C16	120.3(5)
Cl12-Bi2-Cl8	90.23(4)	C25-N6-C21	121.1(7)
Cl9-Bi2-Cl8	89.65(4)	C35-N8-C31	114.9(7)
Cl7-Bi2-Cl8	86.87(4)	C21-C22-C23	119.3(6)
		N6-C25-C24	121.2(7)
		C33-C34-C35	120.5(8)
		C34-C35-N8	119.9(7)
		C32-C31-N8	119.5(8)
		C24-C23-C22	119.6(7)
		C25-C24-C23	120.9(7)
		C31-C32-C33	121.8(10)
		C22-C21-N6	117.9(7)
		C34-C33-C32	123.1(9)
		C30-N7-C26	119.0(8)
		C27-C26-N7	118.3(9)
		C28-C27-C26	118.3(9)
		C27-C28-C29	124.8(9)
		C29-C30-N7	123.1(9)
		C30-C29-C28	116.5(9)

In the same time, the hydrogen atoms bonded to nitrogen atoms participate in the formation of N-H...Cl hydrogen bonding with chlorine atoms of  $\text{BiCl}_6^{3-}$  anions and in the formation of N-H...O hydrogen bonding with to oxygen atoms of isolated nitrate anions (Fig. 3). All of these hydrogen bonds, N-H...Cl and N-H...O (see Table 5) give rise to a three – dimensional network in the structure and add stability of this compound.

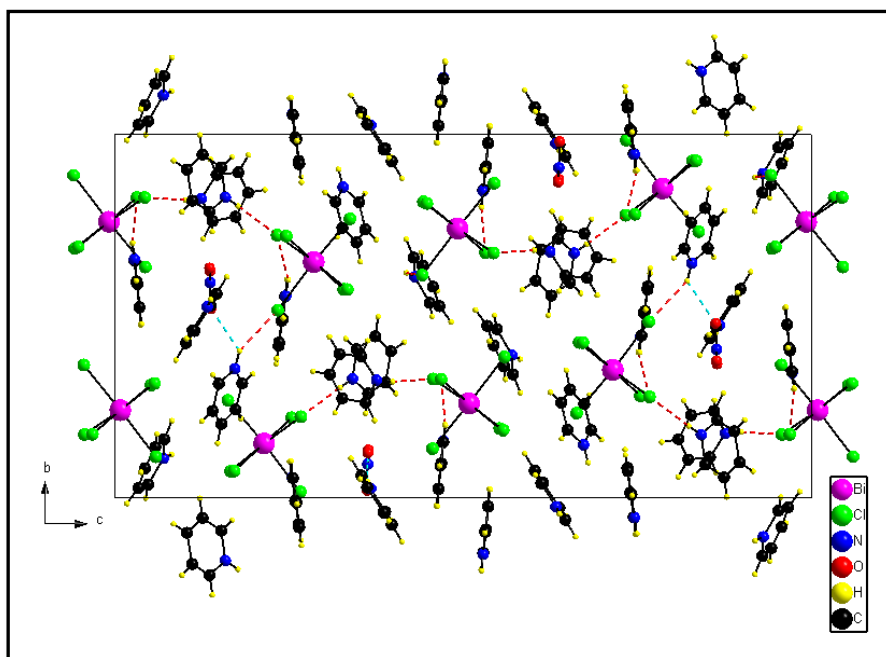

**Figure 3:** Hydrogen bond between the constituents of the structure of  $[\text{C}_5\text{H}_5\text{NH}]_7(\text{BiCl}_6)_2(\text{NO}_3)$  along the axis *a*

**Table 5:** Hydrogen bonds for  $[\text{C}_5\text{H}_5\text{NH}]_7(\text{BiCl}_6)_2(\text{NO}_3)$

D–H...A	d(D–H)	d(H...A)	d(D...A)	<(DHA)
N2–H2...O1	0,860	1,946	2,760	157,44
N2–H2...O2	0,860	2,658	3,401	145,41
N2–H2...N1	0,860	2,676	3,518	166,36
N3–H3...Cl1	0,860	2,867	3,726	177,13
N4–H4A...O2	0,860	2,496	3,148	133,22
N4–H4A...Cl3	0,860	2,942	3,597	134,40
N5–H5A...Cl1	0,860	2,818	3,623	156,55
N6–H6A...Cl8'	0,860	2,616	3,466	169,85
N7–H7A...Cl9	0,860	2,934	3,540	129,15
N8–H8A...Cl10'	0,860	2,664	3,508	167,45

Codes de symétries: (i)  $x-1/2, -y+3/2, z-1/2$

## Conclusion

In this study, a novel organic–inorganic bismuth–chloride based compound with general formula  $[\text{C}_5\text{H}_6\text{NH}]_7(\text{BiCl}_6)_2(\text{NO}_3)$  has been synthesized. Single-crystal X-ray diffraction showed the formation of title compound consisting of two independent octahedra of Bismuth, seven monoprotonated organic cations and isolated nitrate anion. Those components are connected themselves by two types of intermolecular hydrogen bonds.

## ACKNOWLEDGEMENTS

This work is supported by the Tunisian National Ministry of Higher Education and Scientific Research and the Crystallography Group which it is a part of the Laboratory of Crystallography and Materials Science (CRISMAT) Joint Research Unit 6508.





## REFERENCES

- [1] L. Sobczyk, R. Jakubas, J. Zaleski, *Pol. Chem.* 71 (3) (1997) 265.
- [2] H. Ishihara, K. Yamada, T. Okuda, A. Weiss, *Bull. Chem. Soc. Jpn.* 66 (2) (1993) 380.
- [3] A. Kallel, J. W. Bats, *Acta Crystallogr. , Sect.C* 41 (7) (1985) 1022-1024.
- [4] M. Bujak, R. J. Angel, *J. Solid State Chem.* 180 (11) (2007) 3026.
- [5] M. Bujak, R. J. Angel, *J. Phys. Chem.B* 110 (2006) 10322.
- [6] G. Xu, Y. Li, W. Zhou, G. Wang, L. Cai, M. Wang, G. Guo, J. Huang, G. Bator, R. Jakubas, *J. Mater. Chem.* 19(15) (2009) 2179.
- [7] R. Jakubas, U. Krzewska, G. Bator, L. Sobczyk, *Ferroelectrics* 77(1) (1988) 129.
- [8] R. Jakubas, *Solid State Commun.* 60 (4) (1986) 389.
- [9] J. Zaleski, Cz. Pawlaczyk, R. Jakubas, H. -G. Unruh, *J. Phys. : Condens. Mater* 12 (33) (2000) 7509-7521.
- [10] A. Miniewicz, J. Sworakowski, R. Jakubas, M. Bertault, C. Ecolivet, *Ferroelectrics* 94 (1) (1989) 323.
- [11] M. Hall, M. Nunn, M. Beglev, D. Bryan Soverby, *J. Chem. Soc. , Dalton Trans.* 6 (1986) 1231.
- [12] R. Jakubas, Z. Ciunik, G. Bator, *Phys.Rev B* 67 (2) (2003) 241031 – 241036 . art. N° 024103.
- [13] A. Piecha, A. Pietraszko, G. Bator, R. Jakubas, *J. Solid State Chem.* 181 (5) (2008) 1155.
- [14] R. Jakubas, J. Jozkow, G. Bator, *J. Korean Phys. Soc.* 32 (SUPPL 1) (1998) S302.
- [15] J. Jozkow, W. Medycki, J. Zaleski, R. Jakubas, G. Bator, Z. Ciunik, *Phys. Chem. Chem. Phys.* 3 (15) (2001) 3222.
- [16] J. Jozkow, R. Jakubas, G. Bator, A. Pietraszko, *J. Chem. Phys.* 114 (16) (2001) 7239.
- [17] G. Bator, R. Jakubas, J. Baran, *Vib . Spectrosc.* 45 (1) (2007) 36.
- [18] G. M. Sheldrick, *SHELXS-97*, Program for the refinement of crystal structures, 1990.
- [19] G. M. Sheldrick, *SHELXL-97*, Program for the refinement of crystal structures, 1997.
- [20] S. Nasri, F. Zouari and H. El Féki, *J. Chem. Crystallogr.* 38 (2008) 729-732.
- [21] I. Baccar, F. Zouari, N. Chniba-Boudjada and P. Bordet, *Jpn. Soc. Anal. Chem.* 26 (2010) 15-16.
- [22] C. Hrizi, C. Chaker and S. Chaabouni, *Ionics* 17 (2011) 545-553.
- [23] Y. Hua Gao, X. Jia Liu, L. Sun and W.-J. Le, *Acta Crystallogr. E* 67 (2011) 1688.
- [24] G. M. Golzar Hossain, *Acta Cryst. E* 69, (2013) 402.