

## Decomposition of NO<sub>x</sub> and PM emission in Diesel Exhaust by Electrochemical reactor with Multilayered Electrodes

S.Jenoris Muthiya<sup>a</sup>, Senthilkumar Pachamuthu<sup>b</sup>

<sup>a</sup> Department of Automobile Engineering, Madras Institute of technology, Anna University, Chennai, Tamil Nadu, India

<sup>b</sup> Department of Automobile Engineering, Madras Institute of technology, Anna University, Chennai, Tamil Nadu, India

### Abstract

NO<sub>x</sub> emissions are highly poisonous and reactive gas liberated excessively from diesel engines. This work attempts to decrease NO<sub>x</sub> emissions by developing electrochemical reactor. The electrochemical reactor consists of electrochemical cells placed inside it. The electrochemical cells are fabricated by YSZ as an electrolyte middle layer coated with NiO-YSZ as cathode layer and Ag-YSZ as anode layer. The electrochemical cells are tested with diesel exhaust in a single cylinder diesel engine. By passing the variable voltage to the electrochemical cell, it is observed that up to 80% NO<sub>x</sub> reduction, 75% PM reduction and 75% HC reduction was achieved with electrochemical cell. Further by coating the BaO NO<sub>x</sub> storage material, NO<sub>x</sub> reduction was reduced to 85%, PM reduction up to 76% and HC reduction up to 80% was achieved. NO<sub>x</sub> reduction was greater with electrochemical cell -2. The presence of NO<sub>x</sub> storage material causes more NO<sub>x</sub> decompositions in the cathode layers. NO<sub>x</sub> decomposition also increases the oxygen concentrations, which further oxidizes the HC and PM emissions. The increase in NO decomposition was due to the increase in the ionic conductivity of the YSZ substrate. NO<sub>x</sub> reduction by electrochemical cell is a cost effective method.

**Keywords:** Diesel, Biodiesel, Engine, Emission, Electrochemical

### Introduction

Nitrogen oxide (NO and NO<sub>2</sub>) are collectively referred as NO<sub>x</sub>. The oxidation of atmospheric nitrogen at higher temperature in combustion produces NO<sub>x</sub> emission. NO<sub>x</sub> emissions cause serious environmental and health problems. The increase in oxygen concentration, diesel engines produce higher NO<sub>x</sub> emissions [1]. The total concentration of NO<sub>x</sub> emissions in diesel engine exhaust generally ranges from 100 to 1000 ppm. NO<sub>x</sub> emission causes serious problems for human beings, which leads to air way irritation, coughing, Asthma, inflammation and permanent lung damage. In environment NO<sub>x</sub> emissions causes acid rain and photochemical smog [2]. Electrochemical NO<sub>x</sub> reduction is the better concept works well for the reduction of NO<sub>x</sub> during excess oxygen exhaust conditions [3-4]. The fig. 1 shows the mechanism of Electrochemical cell. In this concept by varying the electric potential, NO<sub>x</sub> molecules are reduced to nitrogen gas (N<sub>2</sub>) and oxygen ions (O<sup>2-</sup>) at the cathode. The oxygen in the cathode is ionically transferred over electrolyte and reaches the anode to oxidize the PM deposited in the anode. The concept of Electrochemical NO<sub>x</sub> reduction was first reported by Pancharatnam et al [5] proposed decomposition of NO<sub>x</sub> using ion conducting materials in the cell using Y-ZrO<sub>2</sub> by applying high voltage. Later, Huggins et al [6] proposed the electrochemical NO reduction by using a solid electrolyte cell. In this study, Electrochemical Reduction by electrochemical cells is proposed to reduce NO<sub>x</sub> and PM Simultaneously.

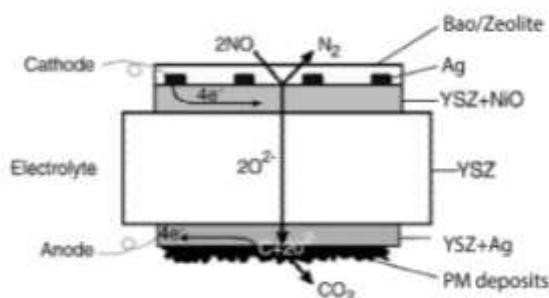


Figure 1. Electrochemical NO<sub>x</sub> reduction Mechanism

### 3. EXPERIMENTAL SECTION

In this current experimentation, (ZrO<sub>2</sub>) (Y<sub>2</sub>O<sub>3</sub>) YSZ was used as the electrolyte. The YSZ powder with polyvinyl alcohol as a binder is mixed and poured into the module. The mixture is pressed in a hydraulic press to form a square plate of 3 mm thickness and 80×80 mm diameter. The YSZ plate is calcined for 7 hours at 1350°C to produce a solid substrate, which is an electrolyte. YSZ is an ionically conducting material and shows better oxygen ion transfer [7, 8]. The cathode material used NiO and YSZ. The cathode material is made into slurry with polyvinyl alcohol and coated on the YSZ disk. The Anode coating is made by using of Ag paste with YSZ by brush coating over the electrolyte. The fig. 2 shows the Electrochemical cell. Fig. 3 shows the scanning electron microscopy of porous electrolyte and electrodes.



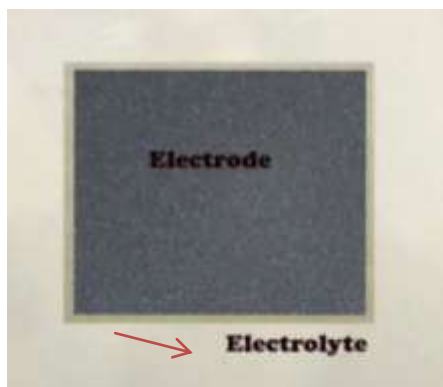


Figure 2. Electrochemical cell

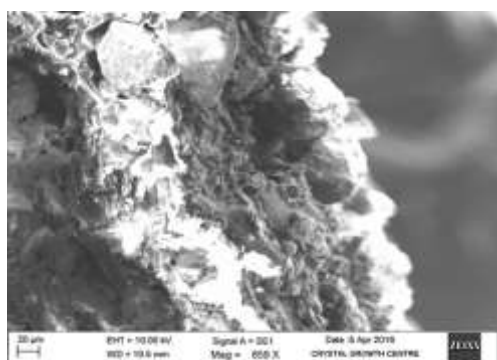

(a)

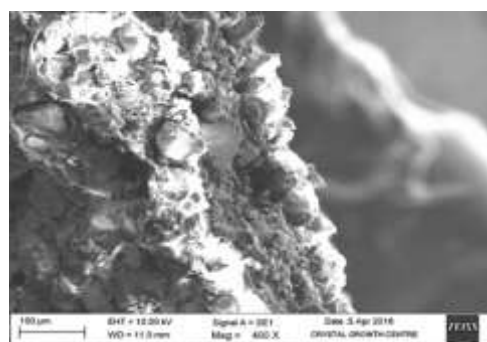

(b)

Figure 3. The Cross Sectional view of manufactured cell (a) Anode and electrolyte (b) Cathode and electrolyte

#### 4. EXPERIMENTAL SET-UP AND TESTING

The experiment was carried out in a single cylinder diesel engine. Fig. 4 shows the experimental set-up of the engine test bench. Initially engine is allowed to run at a constant speed for 10 to 15 minutes at idle load condition until it reaches steady state. The dynamometers were calibrated to avoid loading error. The Electrochemical reactor was fitted to the exhaust pipe with the power supply from the Diesel engine. The NO<sub>x</sub> emissions were measured by using the Chemiluminescence NO<sub>x</sub> analyzer for different load conditions. The cross section of the electrochemical reactor device is shown Fig.6. A 12 V battery was used as a power source to activate the electrochemical reactor. The PM emissions were measured by using micro soot sensor and the AVL di gas analyzer was used to measure HC, CO, and CO<sub>2</sub> emissions.

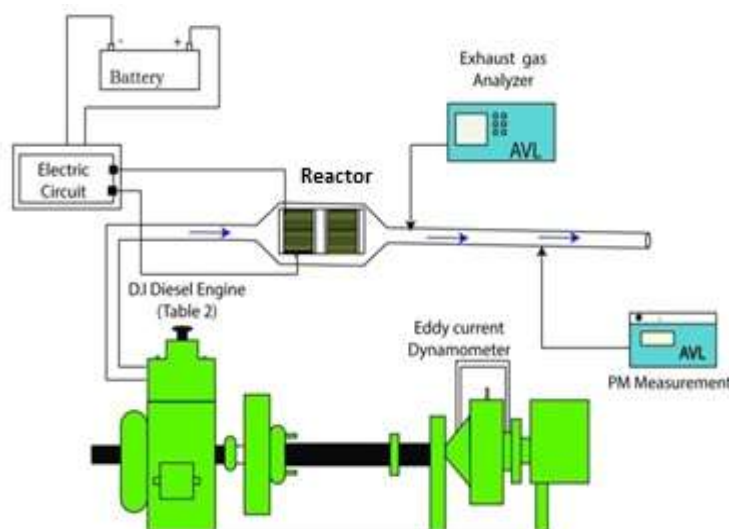


Figure 4. Complete Experimental set-up


## 5. RESULT AND DISCUSSION

The ENAR cell-1 and cell-2 was fabricated with materials -



Ag+YSZ (anode)/ YSZ (electrolyte)/YSZ+ NiO (cathode)/cu-zeolite (NO<sub>x</sub> storage)

Ag+YSZ (anode) / YSZ (electrolyte) / YSZ+ NiO (cathode)/BaO (NO<sub>x</sub> storage)


In Electrochemical cells the decomposition of NO<sub>x</sub> takes place by passing alternating current. The presence of oxygen concentration in diesel exhausts initiates the reduction of O<sub>2</sub> over the electrolyte and is indicated by the reaction



The NO<sub>x</sub> molecules adsorbed on the storage material are decomposed over the electrodes by the reactions.



The cell-1 had the maximum amount of NO decomposition and Polar like NO and CO<sub>2</sub> has more affinity towards zeolite. The three dimensional micro structure of the zeolite inter locks the NO<sub>x</sub> molecule over it. There by supplying electric current to electrode the decomposition of NO<sub>x</sub> takes place over cathode. In cell-2 BaO was used as a NO<sub>x</sub> storage material. NO<sub>x</sub> storage Coating BaO is necessary for the electrochemical reduction of NO<sub>x</sub> [10]. In this technique, Ba is present over the cathode layer in the form of BaO and reacts with NO<sub>x</sub> as indicated by reaction R(5)



The reduction of NO<sub>x</sub> is further achieved by decomposition of Ba (NO<sub>3</sub>)<sub>2</sub> with applied voltage by the reaction R (6)



The Electrochemical reactor was tested with two different combinations of Cells. Fig. 5 Shows the Electrochemical cells tested in real exhaust conditions in diesel engine. The Cell-1 showed better NO<sub>x</sub> reduction over diesel exhaust. The presence of zeolite NO<sub>x</sub> storage material in the Cell-1 increased the decomposition of NO<sub>x</sub> up to 85%. In Cell-2 NO<sub>x</sub> storage material used was BaO. The NO<sub>x</sub> decomposition rate was slightly lower in Cell-2, which was due to the storage capacity of BaO. It was observed that the NO<sub>x</sub> storage coating over the cathode layer was necessary to reduce the NO<sub>x</sub> molecules into N<sub>2</sub>. The decomposed oxygen further oxidized the PM emissions.


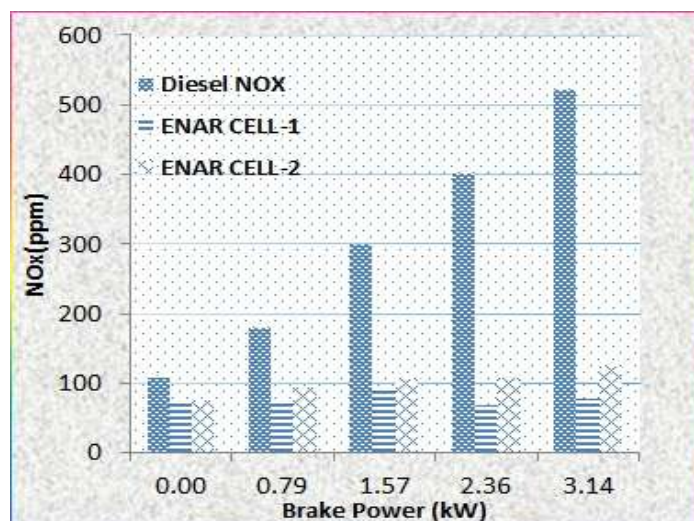


Figure 5. NO<sub>x</sub> emission with respect to engine Brake Power

The exhaust temperature was measured using thermocouple fixed to the exhaust pipe. The exhaust temperature was an important factor for the activation of the catalyst. The NO<sub>x</sub> formation increased with the in-cylinder temperature [9]. The exhaust temperature was further increased by increasing the load. The NO<sub>x</sub> formation also increased with oxygen concentration. Fig. 6 shows the NO<sub>x</sub> emission with respect to exhaust temperature. It was observed that the activation temperature for the catalytic material fell in the range of 150°C-200°C. The Zeolite decomposition started at Cell-1 even at a lower temperature of 150°C. In Cell- 2 the decomposition started at 150°C because the BaO was not effective at temperatures below 200°C.

The decomposition rate is lesser by using BaO because, the CO<sub>2</sub> in the diesel exhaust reacts with the BaO sites to form the reaction





The  $\text{CO}_2$  is can be stored in Ba as shown in R(7).The presence of  $\text{CO}_2$  in the exhaust produces fast production of  $\text{BaCO}_3$ .The  $\text{BaCO}_3$  is finally converted in to  $\text{Ba(NO}_3)_2 + \text{CO}_2$  , as shown in R(8) .The reaction rate of R(8) is slower than R(7) . Therefore  $\text{CO}_2$  is the exhaust will reduce the  $\text{NO}_x$  storage rate with  $\text{BaO}$  there by reduces the decomposition rate of  $\text{NO}_x$  with respect to cell-2.

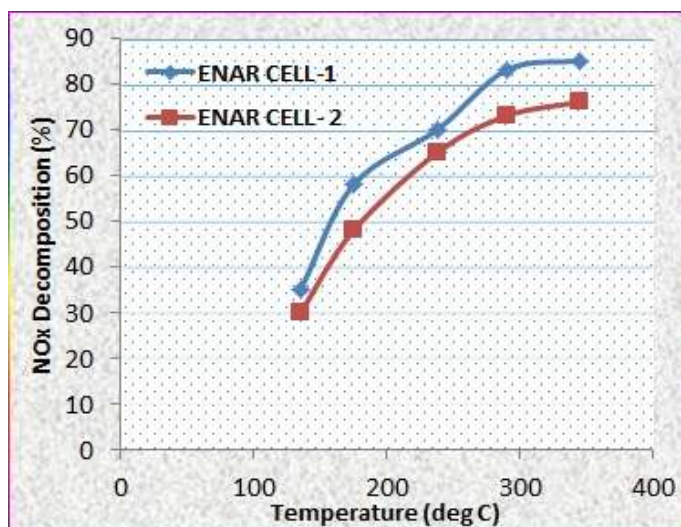


Figure 6.  $\text{NO}_x$  emission with respect to exhaust gas temperature

## 5.1 Simultaneous Reductions

The cells were tested for simultaneous reduction of PM and  $\text{NO}_x$  in the diesel exhaust and they were tested in a single cylinder diesel engine in variable load conditions. Fig. 7.shows the PM oxidation on Electrochemical Cells. The voltage applied to the cell initiated the reduction of  $\text{NO}_x$  and PM oxidation.



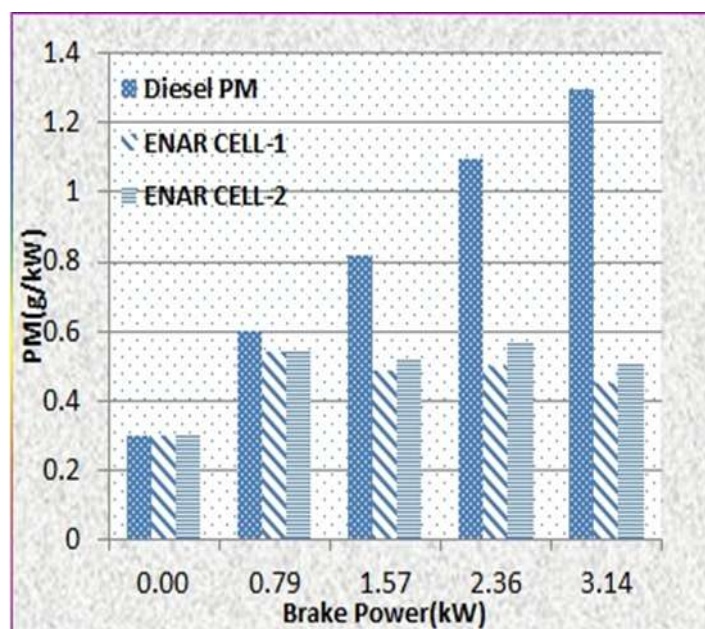


Figure 7. Particulate matter emission with respect to engine Brake power

By applying a current of 0-15 V, PM oxidation and reduction was achieved more than 65%. The PM oxidation increased with Cell-1 because of the maximum  $\text{NO}_x$  storage capacity of zeolite. The decomposition of  $\text{NO}_x$  into  $\text{N}_2$  and  $\text{O}_2$  increased and the decomposed oxygen ions from the electrolyte oxidized the PM deposits effectively on the anode layers.



## Conclusion

This is a vital technique to reduce diesel engine NO<sub>x</sub> emissions. The electrochemical NO<sub>x</sub> reduction for the real exhaust condition was tested. In this technology by passing electric current simultaneous reduction of NO<sub>x</sub> and PM can be achieved. In this method, 80 % reduction of NO<sub>x</sub> and 65% of PM is achieved at the effective temperature of 350°C. The flow rate of exhaust is constant and the temperature varies with increasing loads. It is observed from the results that at 250-350°C are the efficient range for the electrochemical cells for the maximum NO<sub>x</sub> decomposition. Because YSZ is an ionically conducting ceramic, this works efficiently when the surface is heated above 200°C. It was observed that by coating the NO<sub>x</sub> storage material, the NO<sub>x</sub> reduction efficiency increased drastically. The results show zeolite has good NO<sub>x</sub> adsorption capacity even at low temperatures 150°C. Low-temperature operation (150°C) was also achieved by the development of this technique. It is considered that proposed result of emission reduction and low temperature activation can be most suitable technique for light duty vehicles.

## References

- [1] John B. Heywood, Internal combustion engine fundamentals (Tata McGraw Hill)
- [2] Jiafeng Sun., Jerald A. Caton, Timothy J. Jacobs., "Oxides of nitrogen emissions from biodiesel-fuelled diesel engines", Fuel Processing Technology 96 (2012) 237–249
- [3] K. Hamamoto, Y. Fujishiro, and M. Awano, "Intermediate temperature electrochemical reactor for NO<sub>x</sub> decomposition," Journal of The Electrochemical Society, vol. 153, no. 11, p. D167–D170, 2006.
- [4] K. Hamamoto, Y. Fujishiro, and M. Awano, "Low-temperature NO<sub>x</sub> decomposition using an electrochemical reactor," Journal of The Electrochemical Society, vol. 155, no. 8, pp. E109–E111, 2008.
- [5] Pancharatnam S., Huggins R. A., D.M., J. Electrochem. Soc., Vol.122, No.7, (1975) 869.
- [6] T. Gur and R. Huggins., J. Electrochem. Soc., 1979, 126, 1067- 1075.
- [7] W.Y. Henandez., A. Hadjar., M. Klotz., "NO<sub>x</sub> storage capacity of Ytria-stabilized zirconia-based catalysts", Applied catalyst B: Environment 130-131 (2013) 54-56
- [8] Yoshihara Yoshinobu., Yoichi Tsuda., Ritsumekia Univ., "Simultaneous reduction of NO<sub>x</sub> and PM in Diesel exhaust based on electrochemical reaction". SAE Technical Paper., 2010-01-0306.
- [9] M. Awano., S. Bredikhin., A. Aronin., "NO<sub>x</sub> decomposition by electrochemical reactor with electrochemically assembled multilayer electrodes", Solid state ionics., 175 (2004) 605-608.
- [10] Sarohan Park., Hwaseob Song., Heon-Jin Choi., "NO decomposition over the electrochemical cell of lanthanum stannate pyrochlore and YSZ composites electrodes" Solid state ionics., 175 (2004) 625-629.
- [11] Koichi Hamamoto., Yoshinobu., Mansanobu., "Simultaneous removal of nitrogen oxides and diesel soot particulate in nano-structured electrochemical reactor". Solid state ionics., 177 (2006) 2297-2300.
- [12] Dmitry M., Rudkevich & Grigory V. Zyryanov., "Solid-State Materials and Molecular Cavities and Containers for the Supramolecular Recognition and Storage of NO<sub>x</sub>-Species: A Review," Taylor & Francis 35:3, 128-178, DOI:10.1080/02603594.2014.994610
- [13] Peter Broqvist, Henrik Grönbeck, Erik Fridell, Itai Panas., "NO<sub>x</sub> storage on BaO: theory and experiment", Catalysis Today 96 (2004) 71–78
- [14] Marie Lund Traulsen, Kjeld Bøhm Andersen, Kent Kammer Hansen., "NO<sub>x</sub> conversion on LSM15-CGO10 cell stacks with BaO impregnation", Journal of Materials Chemistry 22(23):11792-11800
- [15] Xi Wang, Yixiang Shi, Ningsheng Cai, "Theoretical modeling of NO electrochemical reduction on multifunctional layer electrode by alternating/direct current electrolysis", Electrochimica Acta 152 (2015) 202–215